

# DuPont™ Delrin® 100PE NC010

## ACETAL RESIN

### Product Information

Common features of Delrin® acetal resins include mechanical and physical properties such as high mechanical strength and rigidity, excellent fatigue and impact resistance, as well as resistance to moisture, gasoline, lubricants, solvents, and many other neutral chemicals. Delrin® acetal resins also have excellent dimensional stability and good electrical insulating characteristics. They are naturally resilient, self-lubricating, and available in a variety of colors and speciality grades.

Delrin® acetal resin typically is used in demanding applications in the automotive, domestic appliances, sports, industrial engineering, electronics, and consumer goods industries.

**Delrin® 100PE is a high viscosity acetal homopolymer, an enhanced version of Delrin® 100P with very low VOC emissions for applications in automotive interiors. It has a great combination of strength and toughness and improved processing productivity for injection molding.**

General information	Value	Unit	Test Standard
Resin Identification	POM	-	ISO 1043
Part Marking Code	POM	-	ISO 11469
Rheological properties	Value	Unit	Test Standard
Melt volume-flow rate	2.1	cm <sup>3</sup> /10min	ISO 1133
Temperature	190	°C	ISO 1133
Load	2.16	kg	ISO 1133
Melt mass-flow rate	2.3	g/10min	ISO 1133
Molding shrinkage, parallel	2.2	%	ISO 294-4, 2577
Molding shrinkage, normal	1.9	%	ISO 294-4, 2577
Mechanical properties	Value	Unit	Test Standard
Tensile Modulus	3100	MPa	ISO 527-1/-2
Yield stress	72	MPa	ISO 527-1/-2
Yield strain	25	%	ISO 527-1/-2
Nominal strain at break	45	%	ISO 527-1/-2
Flexural Modulus	2900	MPa	ISO 178
Flexural Stress at 3.5%	79	MPa	ISO 178
Charpy impact strength			ISO 179/1eU
73 °F	N	kJ/m <sup>2</sup>	
-22 °F	380	kJ/m <sup>2</sup>	
Charpy notched impact strength			ISO 179/1eA
73 °F	15	kJ/m <sup>2</sup>	
-22 °F	12	kJ/m <sup>2</sup>	
Hardness, Rockwell, M-scale	91	-	ISO 2039-2
Hardness, Rockwell, R-scale	121	-	ISO 2039-2
Thermal properties	Value	Unit	Test Standard
Melting temperature, 18 °F/min	178	°C	ISO 11357-1/-3
Temp. of deflection under load			ISO 75-1/-2
260 psi	96	°C	
65 psi	157	°C	
Vicat softening temperature, 90 °F, 2 lbf	175	°C	ISO 306
Coeff. of linear therm. expansion, parallel	110	E-6/K	ISO 11359-1/-2
Coeff. of linear therm. expansion			ISO 11359-1/-2
normal	110	E-6/K	
Normal, -40-23 °C	100	E-6/K	
Parallel, -40-23 °C	100	E-6/K	
Flammability	Value	Unit	Test Standard
FMVSS Class	B	-	ISO 3795 (FMVSS 302)
Burning rate, Thickness 1 mm	<100	mm/min	ISO 3795 (FMVSS 302)
Electrical properties	Value	Unit	Test Standard
Relative permittivity			IEC 60250
100Hz	4	-	
1MHz	3.9	-	
Dissipation factor			IEC 60250
100Hz	5	E-4	
1MHz	50	E-4	

Revised: 2017-01-27

Page: 1 of 4

To find out more, visit [DuPont Performance Polymers](#) or contact nearest DuPont location.

North America

Tel: +1 302 999-4592

Toll-Free (USA): 800 441-0575

Asia Pacific

Tel: +81 3 5521 8600

Europe/Middle East/Africa

Tel: +41 22 717 51 11



Copyright 2017 DuPont. The DuPont Oval Logo is a trademark or registered trademark of E.I. du Pont de Nemours and Company or its affiliates. All rights reserved.

# DuPont™ Delrin® 100PE NC010

## ACETAL RESIN

Volume resistivity	>1E13	Ohm*m	IEC 60093
Surface resistivity	3E14	Ohm	IEC 60093
Electric strength	44	kV/mm	IEC 60243-1
Comparative tracking index	600	-	IEC 60112
<b>Other properties</b>	<b>Value</b>	<b>Unit</b>	<b>Test Standard</b>
Humidity absorption, 80mil	0.19	%	Sim. to ISO 62
Water absorption, 80mil	0.92	%	Sim. to ISO 62
Density	1420	kg/m <sup>3</sup>	ISO 1183
Density of melt	1190	kg/m <sup>3</sup>	-
<b>VDA Properties</b>	<b>Value</b>	<b>Unit</b>	<b>Test Standard</b>
Emissions	<2	mg/kg	VDA 275
<b>Injection</b>	<b>Value</b>	<b>Unit</b>	<b>Test Standard</b>
Drying Recommended	yes	-	-
Drying Temperature	80	°C	-
Drying Time, Dehumidified Dryer	2 - 4	h	-
Processing Moisture Content	≤0.2	%	-
Melt Temperature Optimum	205	°C	-
Min. melt temperature	200	°C	-
Max. melt temperature	210	°C	-
Mold Temperature Optimum	90	°C	-
Min. mold temperature	80	°C	-
Max. mold temperature	100	°C	-
Hold pressure range	90 - 110	MPa	-
Hold pressure time	8	s/mm	-
Annealing time, optional	30	min/mm	-
Annealing temperature	160	°C	-
<b>Extrusion</b>	<b>Value</b>	<b>Unit</b>	<b>Test Standard</b>
Drying Temperature	75 - 85	°C	-
Drying Time, Dehumidified Dryer	2 - 4	h	-
Processing Moisture Content	≤0.2	%	-
Melt Temperature Optimum	200	°C	-
Melt Temperature Range	195 - 205	°C	-

### Characteristics

Processing	<ul style="list-style-type: none"> <li>• Injection Molding</li> <li>• Profile Extrusion</li> </ul>	<ul style="list-style-type: none"> <li>• Sheet Extrusion</li> <li>• Other Extrusion</li> </ul>
Delivery form	<ul style="list-style-type: none"> <li>• Pellets</li> </ul>	
Additives	<ul style="list-style-type: none"> <li>• Release agent</li> </ul>	
Regional Availability	<ul style="list-style-type: none"> <li>• North America</li> <li>• Europe</li> </ul>	<ul style="list-style-type: none"> <li>• Asia Pacific</li> <li>• South and Central America</li> </ul>
		<ul style="list-style-type: none"> <li>• Near East/Africa</li> <li>• Global</li> </ul>

### Processing Texts

#### Injection molding

Drying is recommended, but not necessary for newly opened packaging stored in a dry location.

Follow the drying guidelines above in the following cases:

- If moisture is above the Processing Moisture Content recommendation,
- When a resin container is damaged,
- When the material is not properly stored in a dry place at room temperature, or
- When packaging stays open for a significant time.

To find out more, visit [DuPont Performance Polymers](#) or contact nearest DuPont location.

#### North America

Tel: +1 302 999-4592

Toll-Free (USA): 800 441-0575

#### Asia Pacific

Tel: +81 3 5521 8600

#### Europe/Middle East/Africa

Tel: +41 22 717 51 11




# DuPont™ Delrin® 100PE NC010


## ACETAL RESIN

### Diagrams

#### Viscosity-shear rate

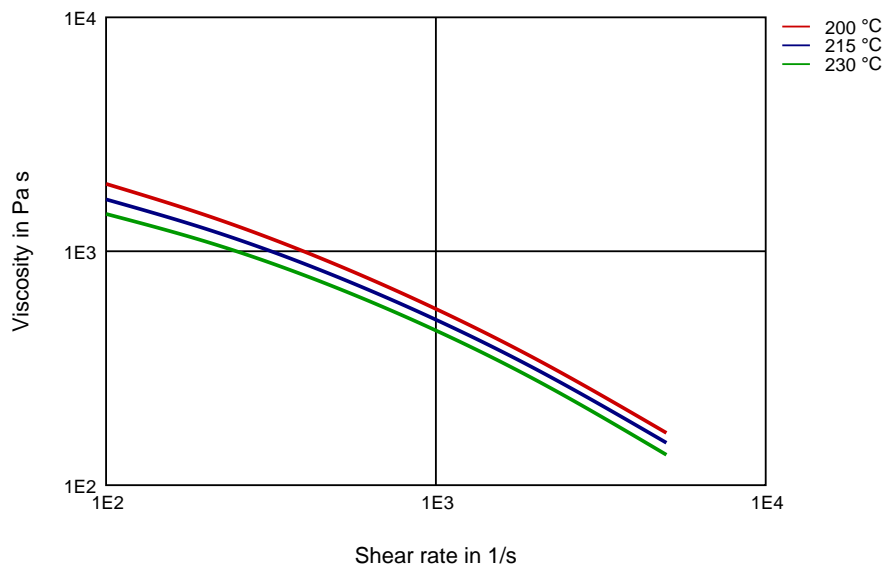

#### Shearstress-shear rate

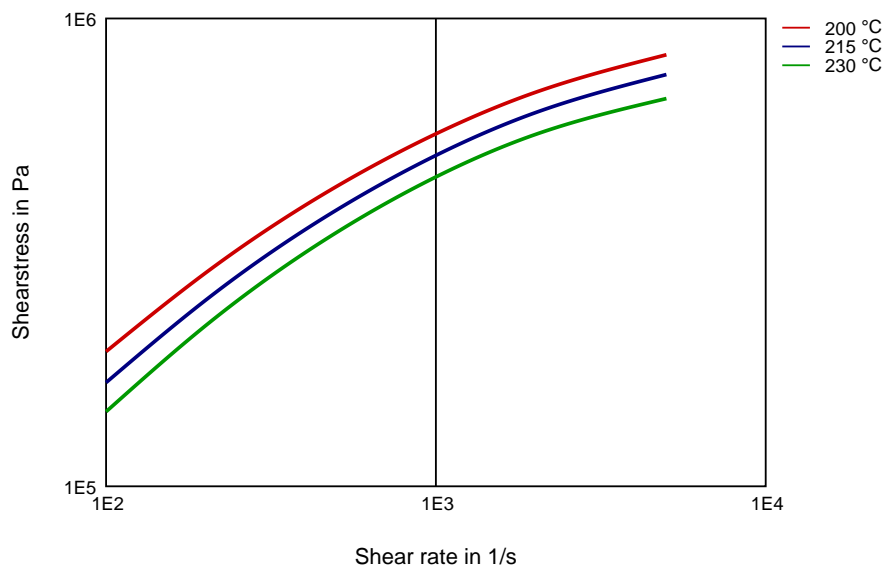

To find out more, visit [DuPont Performance Polymers](#) or contact nearest DuPont location.

#### North America

Tel: +1 302 999-4592

Toll-Free (USA): 800 441-0575

#### Asia Pacific

Tel: +81 3 5521 8600

#### Europe/Middle East/Africa


Tel: +41 22 717 51 11



# DuPont™ Delrin® 100PE NC010

## ACETAL RESIN

### Tensile modulus-temperature

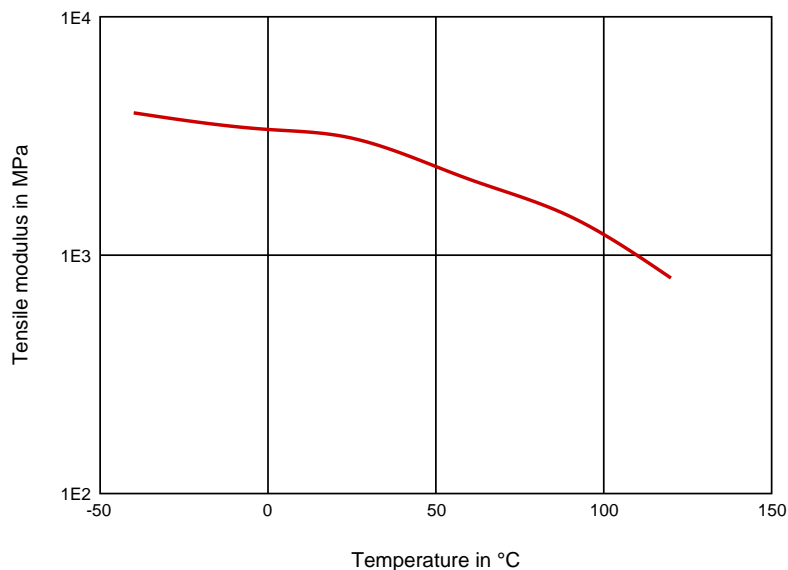

Contact DuPont for Material Safety Data Sheet, general guides and/or additional information about ventilation, handling, purging, drying, etc. ISO Mechanical properties measured at 160 mil (Hytrel® measured at 80 mil), IEC Electrical properties measured at 80 mil, all ASTM properties measured at 120 mil, and test temperatures are 73°F unless otherwise stated.

The information set forth herein is furnished free of charge and is based on technical data that DuPont believes to be reliable and falls within the normal range of properties. It is intended for use by persons having technical skill, at their own discretion and risk. This data should not be used to establish specification limits nor used alone as the basis of design. Handling precaution information is given with the understanding that those using it will satisfy themselves that their particular conditions of use present no health or safety hazards. Since conditions of product use and disposal are outside our control, we make no warranties, express or implied, and assume no liability in connection with any use of this information. As with any product, evaluation under end-use conditions prior to specification is essential. Nothing herein is to be taken as a license to operate or a recommendation to infringe on patents. Caution: Do not use in medical applications involving permanent implantation in the human body. For other medical applications, discuss with your DuPont customer representative and read Medical Caution H-50103-5.

Copyright © 2017 DuPont or its affiliates. All Rights Reserved. The DuPont Oval Logo, DuPont™, The miracles of science™ and all products denoted with ® or ™ are registered trademarks or trademarks of E.I. du Pont de Nemours and Company or its affiliates.

To find out more, visit [DuPont Performance Polymers](#) or contact nearest DuPont location.

#### North America

Tel: +1 302 999-4592

Toll-Free (USA): 800 441-0575

#### Asia Pacific

Tel: +81 3 5521 8600

#### Europe/Middle East/Africa

Tel: +41 22 717 51 11

